



RESEARCH ARTICLE

INNOVATIVE GREEN SYNTHESIS AND CHARACTERIZATION OF COW URINE-DERIVED CUPROUS OXIDE NANOPARTICLES FOR ANTI-MICROBIAL ACTIVITY

Imbabazizayo Prosper^{1,2} , Tuyizere Aime² , Harshil Majethia² 

¹Rwanda Food and Drug Authority, Rwanda.

²Department of Pharmaceutical Science, Marwadi University, Rajkot, Gujarat, India.

Article Info:

Abstract



Article History:

Received: 3 February 2026

Reviewed: 11 March 2026

Accepted: 12 April 2026

Published: 15 May 2026

Cite this article:

Prosper I, Aime T, Majethia H. Innovative green synthesis and characterization of cow urine-derived cuprous oxide nano-particles for anti-microbial activity. Universal Journal of Pharmaceutical Research 2026; 11(2): 31-35. <http://doi.org/10.22270/ujpr.v11i2.1532>

*Address for Correspondence:

Imbabazizayo Prosper, Rwanda Food and Drug Authority, Rwanda. Tel: +250783661200
 E-mail: zayopros@gmail.com

Background: The rise in bacteria resistant to antibiotics is a serious global health problem, pushing the search for new ways to fight them. Using green synthesis to synthesize nanoparticles is a sustainable alternative to traditional, more polluting methods. This research looks at using cow urine, a natural resource with components that can help in the synthesis, to create cuprous oxide (Cu₂O) nanoparticles.

Methods: Nanoparticles were synthesized through a simple green process that uses cow urine and ascorbic acid to reduce the starting materials. Then, we used several techniques UV-Vis spectroscopy, FTIR, and Zeta potential/DLS – to check the nanoparticles and find out their properties like size and stability. Finally, we tested how well the nanoparticles could kill/deactivate *Staphylococcus aureus* and *Escherichia coli* bacteria.

Results: The tests confirmed presence of Cu₂O nanoparticles, with a key absorbance at 419 nm. FTIR showed the presence of Cu-O bonds and other chemical groups. The nanoparticles were moderately stable, with a zeta potential of -4.732 mV, and their size was around 271.3 nm. They were effective against both bacteria, but *S. aureus* was more sensitive to them.

Conclusion: This study shows that it's possible to produce Cu₂O nanoparticles in a green and easy way using cow urine and ascorbic acid. These nanoparticles can effectively fight bacteria, suggesting they could be a valuable tool in the fight against antibiotic resistance and a more sustainable approach to making nanomaterials.

Keywords: Antimicrobial activity, ascorbic acid, cow urine, cuprous oxide nanoparticles, green synthesis.

INTRODUCTION

The domain of nanotechnology has experienced a notable transition towards environmentally sustainable synthesis methodologies. This shift is motivated by the imperative to mitigate environmental toxicity, decrease energy expenditure, and leverage renewable sources in the fabrication of nanoparticles^{1,2}. Within the spectrum of metal oxides, cuprous oxide nanoparticles have attracted substantial scientific attention owing to their distinctive physicochemical characteristics and diverse applications spanning catalysis, biosensing, anti-microbial interventions, and Oncological therapeutics^{3,4}. Conventional synthesis techniques frequently employ hazardous solvents and elevated temperatures, presenting ecological and biological hazards, thereby underscoring the necessity for the investigation of environmentally friendly synthesis

strategies^{5,6}. Contemporary research has increasingly concentrated on the utilization of biological substrates, encompassing plant extracts, microorganisms, and animal-derived materials, to facilitate the biogenic synthesis of nanoparticles⁷. An especially promising and relatively underexplored biogenic resource in this context is cow urine, which comprises a complex mixture of bioactive constituents, including urea, creatinine, phenolic compounds, enzymes, and a variety of inorganic minerals⁸. The aforementioned components of cow urine demonstrate inherent reducing, capping, and stabilizing capacities, positioning it as a sustainable and economically viable substitute for synthetic chemical precursors. In the present investigation, ascorbic acid was employed in conjunction with cow urine⁹. Ascorbic acid is a recognized environmentally friendly reducing agent, and its combined application with cow urine is

hypothesized to augment the reduction kinetics and stabilization of Cu^{2+} ions, thereby facilitating enhanced nanoparticle synthesis¹⁰. The present study is designed to synthesize and characterize Cu_2O nanoparticles utilizing an optimized biogenic synthesis approach that incorporates cow urine and ascorbic acid, obviating the requirement for exogenous capping ligands such as cetyltrimethyl ammonium bromide or polyvinyl pyrrolidone¹¹. Although prior investigations have explored the application of plant-derived materials in Cu_2O synthesis, the synergistic utilization of cow urine in conjunction with ascorbic acid in this process constitutes a largely uninvestigated area, thereby representing a novel contribution to the advancement of sustainable nanotechnology¹². This research endeavor not only advocates for a cost-effective and ecologically sound methodology for nanoparticle formation but also valorizes a naturally occurring biological waste product, aligning with the fundamental tenets of green chemistry and the circular bioeconomy.

MATERIALS AND METHODS

Cuprous Oxide nanoparticles were synthesized based on the different studies with some modification. The Cu_2O nanoparticles were synthesized by starch-reduction approach. First, 0.1 M copper sulfate (CuSO_4) solution was mixed with 120 mL of 1.2% starch solution under continuous stirring of 400 rpm for 30 minutes in order to get homogeneous mixture. Secondly, 50 mL of 0.2M ascorbic acid solution, which was prepared using cow urine, was gradually mixed with the reaction mixture with continuous stirring. Ascorbic acid served as a reducing agent in the process of nanoparticle preparation. Thirdly, 30 mL of 1M sodium hydroxide solution was dropped in the mixture while continuously stirring. The whole reaction was conducted under continuous stirring conditions for 2 hours at 80°C to facilitate the synthesis of cuprous oxide nanoparticles. Once the reaction was completed, the solution was taken off heat source and kept overnight under room temperature conditions. Then,

the solution was filtered to get cuprous oxide nanoparticles that were formed during the reaction. These nanoparticles were washed three times with deionized water and ethanol in order to get rid of the unreacted substances and impurities. Finally, the dried nanoparticles were subjected to oven-drying at 40°C for one hour followed by grinding them for 30 minutes using mortar and pestle¹³.

Characterization of cuprous oxide nanoparticles: As nanomaterials are beyond the perception of human eyes, it becomes impossible to visualize its morphology and nature. Consequently, it becomes indispensable to analyze the synthesized substances utilizing sophisticated characterization methodologies. To date, no chemical analytical pathways are routinely employed; therefore, reliance on physical methods of analysis is necessary. Researchers commonly utilize physical techniques for the examination of nanomaterials. While physical analysis methods can be costly and necessitate skilled personnel for operation, contemporary instrumentation can precisely determine the dimensions of materials, and electron micrographs can elucidate the morphology of nanomaterials. Many advanced research institutions now possess these facilities. The array of characterization techniques includes ultraviolet-visible spectroscopy, X-ray diffraction, electron microscopy, zeta potential measurement, and dynamic light scattering, among others¹⁴.

Antimicrobial assays: Antibacterial activity of synthesized Cu_2O nanoparticles was tested by employing agar well diffusion technique. Sterilization process was performed under the following conditions: liquid Mueller Hinton agar medium and Petri dishes were subjected to autoclaving in an autoclave machine at 121°C , 15 psi, for a period of 30 minutes. Following this, 4 mm thick layers of sterile agar medium were poured into Petri dishes. Prior to inoculation of agar medium, 18 hours' cultures of *S. aureus* and *E. coli* were evenly spread onto the surface of the agar plates. Wells were formed on agar plates using a sterile cork borer and different concentrations of Cu_2O nanoparticles and amoxicillin (control) were added to these wells¹⁵.

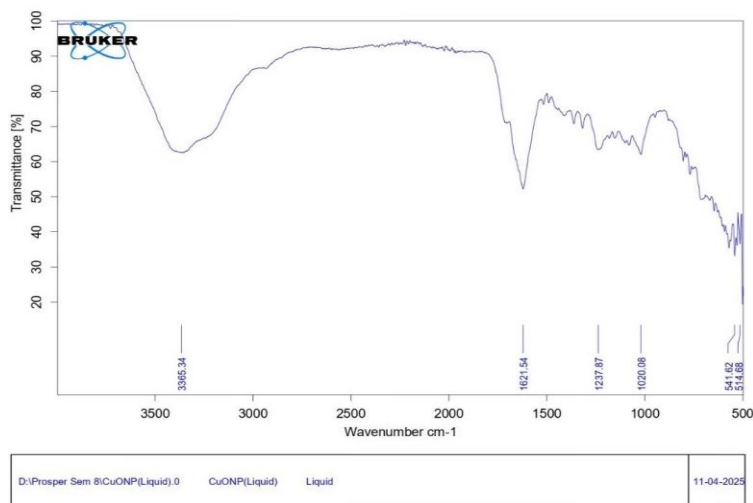


Figure 1: FTIR analysis of synthesized Cu_2O nanoparticles.

RESULTS AND DISCUSSION

The successful synthesis of copper oxide nanoparticles (nanoparticulated Cu₂O) was confirmed by the application of UV-visible and Fourier Transform Infrared Spectroscopy (FTIR). In particular, during the current research, the use of UV-Visible spectroscopy was performed, and a characteristic absorption peak was found at the wavelength of 419 nm. The latter corresponds quite well with the absorption range of Cu₂O nanoparticles, mentioned in scientific literature and proves the synthesis of the necessary semi-conductors. As it can be seen, an absorption peak at 419 nm describes the optical properties and electronic

transitions of nanocrystalline copper oxide. At the same time, the results of FTIR analysis prove the successful synthesis of Cu₂O nanoparticles through a particular characteristic of the Cu-O bond stretch at 1020.08 cm⁻¹. Moreover, the presence of a wide absorption band at 3365.34 cm⁻¹ is attributed to the O-H bond stretch, and it means the adsorption of water molecules from the atmosphere on the nanoparticles' surface¹⁶. Furthermore, the peaks at 1621.54 cm⁻¹ and 1237.87 cm⁻¹ are explained by the carbon-containing functional groups that might have been introduced into the sample in the process of synthesis from starch. In this way, the results prove that the molecules of starch were involved in the formation of nanoparticles¹⁷.

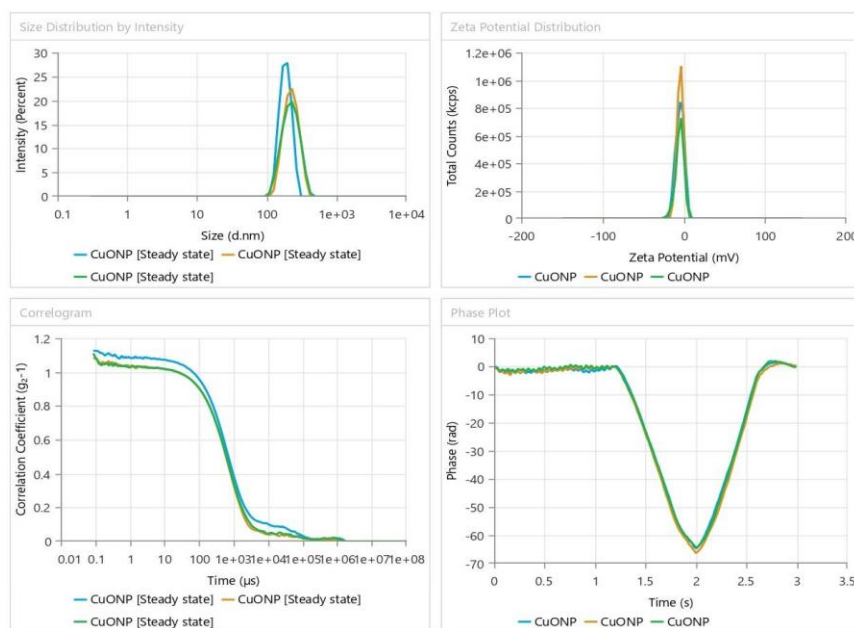


Figure 2: Particle size analysis of synthesized nanoparticles.

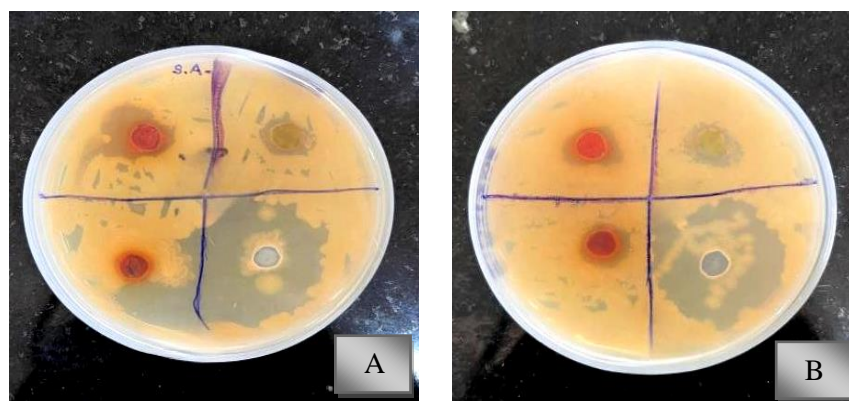


Figure 3: Inhibition of bacteria growth by Cu₂O NPs in (A): *S. aureus* and (B): *E. coli*.

Moreover, particle size and zeta potential analysis were carried out. Particle size analysis showed that the obtained nanoparticles had a hydrodynamic diameter of 271.3 nm with a relatively high degree of polydispersity. It might mean that the nanoparticles tend to aggregate, probably, because of poor electrostatic repulsion between particles¹⁸. At the same time, the relatively low zeta potential (-4.732 mV) indicates insufficient electrostatic repulsion between the particles. However, the obtained data still allows claiming that the nanoparticles demonstrate good

colloid stability owing to the adsorption of starch molecules¹⁹. It is important to mention that a large hydrodynamic diameter seems unexpected. Based on the antibacterial properties of the prepared nanoparticles, it was shown that the nanoparticles were capable of inhibiting the growth of both *S. aureus* and *E. coli*. Thus, the broad antibacterial properties of the produced nanoparticles were proven. Moreover, it was established that minimum inhibitory concentrations (MIC) against *S. aureus* were 3 mg/mL, while for *E. coli*, they were 10 mg/mL^{20,21}. It means that Gram-

positive bacteria were proven to be more sensitive than Gram-negative bacteria to the influence of Cu₂O nanoparticles, whereas Gram-negative strains were less sensitive. It may be attributed to the fact that the outer layer of the structure of Gram-negative bacteria decreases nanoparticle penetration and antibacterial activity²². Concerning the mechanism of the antibacterial properties of synthesized Cu₂O nanoparticles, it includes the release of copper ions (Cu⁺ and Cu²⁺), as well as the formation of ROS, resulting in oxidation. It causes the disruption of membranes, damages proteins and nucleic acids, and finally, leads to cell death²³. In conclusion, the conducted research demonstrated the efficiency of the proposed starch-assisted method in obtaining nanoparticles with biological activity. Besides, it provided proof of the chemical and structural composition of nanoparticles and antibacterial activity. Using environmentally friendly stabilizers is an adequate solution to overcome disadvantages of traditional nanoparticle synthesis approaches. Despite the great number of previous studies on the impact of nanoparticles based on copper oxides, the present research provides valuable information regarding antibacterial properties of nanoparticles. Therefore, it can be concluded that it opens interesting perspectives for the usage of nanoparticles with starch in different fields. Nonetheless, further research is needed for evaluation of safety, efficacy, and possible practical applications of Cu₂O nanoparticles with starch.

CONCLUSIONS

This study successfully developed a green and scalable method for making cuprous oxide (Cu₂O) nanoparticles. The process used cow urine and ascorbic acid, offering a more sustainable alternative to traditional chemical synthesis by cutting down on the use of harmful chemicals and energy. The resulting Cu₂O nanoparticles showed good antibacterial activity against both Gram-positive (*S. aureus*) and Gram-negative (*E. coli*) bacteria, with *S. aureus* being more sensitive. These findings suggest that Cu₂O nanoparticles made through this eco-friendly approach could be useful as antibacterial agents to fight antibiotic resistant bacteria. Moreover, this research points to the potential of using biological waste, like cow urine, to produce valuable nanomaterials, which fits well with the principles of green nanotechnology and a circular economy. Future research could explore the *in-vivo* applications of these nanoparticles and optimize the synthesis for even greater yield and stability.

ACKNOWLEDGEMENTS

The authors sincerely thank the Marwadi University Faculty of Pharmacy for providing the laboratory facilities and technical assistance throughout this study. Special gratitude is extended to the colleagues and staff for their support during the formulation and analytical procedures. Finally, appreciation goes to all who contributed directly or indirectly to the successful completion of this research.

AUTHOR'S CONTRIBUTIONS

Prosper I: writing the original draft, methodology, investigation. **Aime T:** conceptualization, literature survey, data processing. **Majethia H:** editing, data curation, methodology, investigation. Final manuscript was checked and approved by all authors.

DATA AVAILABILITY

The datasets generated or analyzed during this study are available from the corresponding author upon reasonable request.

CONFLICTS OF INTEREST

None to declare.

REFERENCES

- Rathod S, Preetam S, Pandey C, Bera SP. Exploring synthesis and applications of green nanoparticles and the role of nanotechnology in wastewater treatment. *Biotechnol Rep* 2024; 41:e00830. <https://doi.org/10.1016/j.btre.2024.e00830>
- Wasiq M, Ahmed F, Saeed F, *et al.* From waste to wellness: Green synthesis of nanoparticles from vegetable waste. *Sustainable Environment* 2025; 11:1. <https://doi.org/10.1080/27658511.2025.2491870>
- Pellosi DS, Paiva GSM, Vital VG, *et al.* Harnessing copper nanoparticles for antimicrobial applications: Advances and challenges. *Antibiotics* 2025; 14(11): 1170. <https://doi.org/10.3390/antibiotics14111170>
- Rajamma RS, Nair G, Khaddar FA, *et al.* Antibacterial and anticancer activity of biosynthesized Cu₂O nanoparticles. *IET Nanobiotechnol* 2020; 14(9): 833-838. <https://doi.org/10.1049/iet-nbt.2020.0088>
- Álvarez-Chimal R, Ángel Arenas-Alatorre J. Green synthesis of nanoparticles: A biological approach. In *Green chemistry for environmental sustainability - Prevention-assurance-sustainability (P-A-S) approach*. Intech Open 2023; <https://doi.org/10.5772/intechopen.1002203>
- Mayegowda BS, Roy ANGM, Pandit S, *et al.* Eco-friendly synthesized nanoparticles as antimicrobial agents: An updated review', *Front Cell Infect Microbiol* 2023; 13: 1224778. <https://doi.org/10.3389/fcimb.2023.1224778>
- Karunakaran G, Sudha KG, Ali S, *et al.* Biosynthesis of nanoparticles from various biological sources and its biomedical applications. *Molecules* 2023; 28(11): 4527. <https://doi.org/10.3390/molecules28114527>
- Sarvalkar PD, Mandavkar RR, Nimbalkar MS, *et al.* Biomimetic synthesis of catalytically active nano-silver using *Bos taurus* (A-2) urine. *Sci Rep* 2021; 11:16934. <https://doi.org/10.1038/s41598-021-96335-2>
- Pelesinuo KB, Sattanathan G, Haque N, *et al.* Synthesis and characterization of Mithun (*Bos frontalis*) urine-based antibacterial copper oxide nanoparticles. *Biomedicines* 2023; 11(6): 1690. <https://doi.org/10.3390/biomedicines11061690>
- Jiang R, Sui Y, Hong J, Niimi M, *et al.* The combined administration of vitamin C and copper induces a systemic oxidative stress and kidney injury. *Biomolecules* 2023; 13:1. <https://doi.org/10.3390/biom13010143>
- Rojas-Jaimes J, Asmat-Campos D. Cu₂O, ZnO, and Ag/Cu₂O nanoparticles synthesized by biogenic and chemical route and their effect on *Pseudomonas aeruginosa* and *Candida albicans*. *Sci Rep* 2023; 13:21478. <https://doi.org/10.1038/s41598-023-47917-9>
- Alhumaimess MS, Essawy AA, Kamel MM, *et al.* Biogenic-mediated synthesis of mesoporous Cu₂O/CuO nano-architectures of superior catalytic reductive towards nitroaromatics. *Nanomaterials* 2020; 10(4): 781. <https://doi.org/10.3390/nano10040781>

13. Aslam MS. Long chain polymeric carbohydrate dependent nanocomposites in tissue engineering. *Universal J Pharm Res* 2020; 5(4):65-70. <https://doi.org/10.22270/ujpr.v5i4.441>
14. Nadeem A, Saqib Z, Arif A, *et al.* Hybrid hydrogels incorporating nanoparticles, their types, development, and applications: A comprehensive review of nanogels. *Universal J Pharm Res* 2024; 9(5): 142-149. <http://doi.org/10.22270/ujpr.v9i5.1202>
15. Balouiri M, Sadiki M, Ibensouda SK. Methods for *in vitro* evaluating antimicrobial activity: A review. *J Pharm Anal* 2016; 6(2):71-79. <https://doi.org/10.1016/j.jpha.2015.11.005>
16. Horti NC, Kamatagi MD, Patil NR, *et al.* Synthesis and optical properties of copper oxide nanoparticles: Effect of solvents. *J Nanophotonics* 2020; 14(4): 046010. <https://doi.org/10.1117/1.JNP.14.046010>
17. Amir RM, Anjum FM, Khan MI, *et al.* Application of Fourier transform infrared (FTIR) spectroscopy for the identification of wheat varieties. *J Food Sci Technol* 2013; 50(5):1018-1023. <https://doi.org/10.1007/s13197-011-0424-y>
18. Sun H, Jiao R, An G, *et al.* Influence of particle size on the aggregation behavior of nanoparticles: Role of structural hydration layer. *J Environ Sci* 2021; 103:33-42. <https://doi.org/10.1016/j.jes.2020.10.007>
19. Hasrawati A, Rizaldi I, Bakri NA, Febrianti D, Mursyid AM. Preparation and characterization of thymoquinone nanoparticles PEGylated as drug delivery system. *Universal J Pharm Res* 2020; 5(6):13-17. <https://doi.org/10.22270/ujpr.v5i6.506>
20. Parvekar P, Palaskar J, Metgud S, *et al.* The minimum inhibitory concentration and minimum bactericidal concentration of silver nanoparticles against *Staphylococcus aureus*. *Biomater Investig Dent* 2020; 7(1): 105-109. <https://doi.org/10.1080/26415275.2020.1796674>
21. Alhamvi S, Akgul B, Akmayan I, *et al.* Size dependent inherent antibacterial activity of polycation coated poly(lactide-co-glycolide) nanoparticles. *Eur Polym J* 2024; 207. <https://doi.org/10.1016/j.eurpolymj.2024.112854>
22. Emami-Karvani Z. Antibacterial activity of ZnO nanoparticle on Gram-positive and Gram-negative bacteria. *Afr J Microbiol Res* 2012; 5:18. <https://doi.org/10.5897/AJMR10.159>
23. Ma X, Zhou S, Xu X, *et al.* Copper-containing nanoparticles: Mechanism of antimicrobial effect and application in dentistry: A narrative review. *Front Surg* 2022; 9:905892. <https://doi.org/10.3389/fsurg.2022.905892>